Pressure-Induced Antiferromagnetic Bulk Superconductor $EuFe_2As_2$

Taichi Terashima[a,c], Hiroyuki S. Suzuki[a], Megumi Tomita[a], Motoi Kimata[a], Hidetaka Satsukawa[a], Atsushi Harada[a], Kaori Hazama[a], Takehiko Matsumoto[a], Keizo Murata[b], Shinya Uji[a,c]

[a] *National Institute for Materials Science, Tsukuba, Japan*
[b] *Division of Molecular Materials Science, Graduate School of Science, Osaka City University, Osaka, Japan*
[c] *JST, Transformative Research-Project on Iron Pnictides (TRIP), Tokyo, Japan*

arXiv:0908.2280v1 [cond-mat.supr-con] 17 Aug 2009

Abstract

We present the magnetic and superconducting phase diagram of $EuFe_2As_2$ for $B \parallel c$ and $B \parallel ab$. The antiferromagnetic phase of the Eu^{2+} moments is completely enclosed in the superconducting phase. The upper critical field vs. temperature curves exhibit strong concave curvatures, which can be explained by the Jaccarino-Peter compensation effect due to the antiferromagnetic exchange interaction between the Eu^{2+} moments and conduction electrons.

Key words: $EuFe_2As_2$, iron pnictides, pressure-induced superconductivity
PACS: 74.62.Fj, 74.25.Dw

Since the discovery of superconductivity (SC) at a transition temperature T_c = 26 K in $LaFeAsO_{1-x}F_x$ by Kamihara *et al*.[1] extensive studies of SC in layered iron pnictides and related compounds have been performed. There were some reports that the 122 parent compounds AFe_2As_2 (A = Ca, Sr, Ba, and Eu) could be tuned to SC by the application of high pressure P [2, 3, 4, 5, 6, 7, 8, 9]. However, most of these reports were based only on resistivity measurements and hence could not establish the bulk nature of P-induced SC. Recently, we have proved from ac magnetic susceptibility measurements that P-induced *bulk* SC does occur in $EuFe_2As_2$ and further that it coexists with the antiferromagnetic order of the Eu^{2+} moments below T_N ($< T_c$) [10]. P-induced bulk SC has also been confirmed for $SrFe_2As_2$ [11]. The occurrence of the bulk SC in the parent compounds has an important implication: the key to SC in the iron pnictides is not carrier doping but suppression of the magnetic/structural transition. Here we present B_{appl} (applied magnetic field)-T (temperature) phase diagrams of $EuFe_2As_2$ for $P \sim 26$ kbar.

Figure 1 shows ac magnetic susceptibility along the c axis of $EuFe_2As_2$ at P = 25.7 kbar. (We recalibrated Manganin wire used for pressure gauges after the publication of Ref. [10] and found that the pressure was estimated about 9% larger in Ref. [10]. For the pressures of 28 and 29 kbar of the c-axis and ab-plane susceptibility measurements in Ref. [10], read 25.7 and 26.3 kbar, respectively.) The susceptibility at zero field exhibits a large drop below T_c = 31 K, then increases with decreasing T to show a peak around T_N = 21 K, where the Eu^{2+} moments order antiferromagnetically, and finally decreases again. The size of diamagnetism is consistent with 100% shielding. With increasing B_{appl}, the superconducting transition shifts to lower T. The feature associated with T_N is barely visible at B_{appl} = 0.25 T, but is already absent at B_{appl} = 0.5 T. The susceptibility vs. B_{appl} curves for $T < T_N$ show drops at low fields. It indicates a field-induced transition from the antiferromagnetic to paramagnetic state of the Eu^{2+} moments. The characteristic field B_m for this transition is defined in the figure. (The definitions of T_N and B_m given in Fig. 1 are different from conventional ones. They have been adopted for practical purposes.) In the case of the a-axis susceptibility, the zero-field curve shows a plateau below T_N, and hence we define T_{N2} as the lower end temperature of the plateau.

Figure 2 shows the B_{appl}-T phase diagrams for $B \parallel c$ and $B \parallel ab$. The antiferromagnetic phase is completely enclosed within the superconducting phase. The upper critical field "B_{c2}" shows peculiar temperature dependence (the quotation marks attached to B_{c2} indicate that B_{c2} values are based on the applied field, not on the internal field). Initially, "B_{c2}" increases rather slowly compared to P or doping-induced SC in other 122 compounds, and then it starts to increase rapidly approximately below zero-field T_N, resulting in pronounced concave curvatures of the "B_{c2}" -T curves. This can be explained by the Jaccarino-Peter compensation effect [12]. For the sake of qualitative discussion, we follow the approximation used in Ref. [13]: $H_{c2} = H^*_{c2} - a[H_{c2} - |H_J|]^2$, where H_{c2} is the upper critical field, H^*_{c2} the orbital critical field, H_J the antiferromagnetic exchange field acting on the conduction electrons, and a determines the strength of the paramagnetic pairbreaking. Although $EuFe_2As_2$ orders antiferromagnetically, the predominant interaction between the Eu^{2+} moments is (inplane) ferromagnetic one [14]. Thus the susceptibility rapidly increases as T approaches T_N from above. Since H_J is proportional to the magnetization of the Eu^{2+} moments, it also increases rapidly. This rapid increase in H_J suppresses H_{c2} relative to H^*_{c2} in the temperature range between T_c and approximately T_N. This explains the initial slow increase in "B_{c2}". On the other hand, below $\sim T_N$ the magnetization saturates at low fields and hence H_J in the above equation is approximately constant. Then, as T is lowered, H_{c2} increases, which *reduces* the pair breaking (as

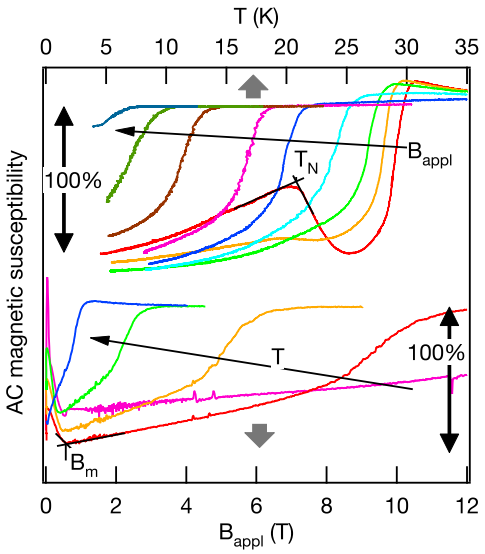

Figure 1: (Color online) AC magnetic susceptibility along the *c*-axis of $EuFe_2As_2$ at P = 25.7 kbar as a function of T at a constant B_{appl} (upper) and as a function of B_{appl} at a constant T (lower). B_{appl} was applied parallel to the *c*-axis. The arrows indicate 100% shielding. For the upper curves, B_{appl} = 0, 0.25, 0.5, 1, 2, 4, 8, 12, and 16 T. For the lower curves, T = 0.02, 10, 15, 20, and 25 K. The definitions of T_N and B_m are shown.

long as $H_{c2} < |H_J|$), which in turn increases H_{c2}, and so on. This leads to a rapid rise in H_{c2} below $\sim T_N$ as is observed.

In summary, we have determined the B_{appl}-T phase diagrams of $EuFe_2As_2$ for $B \parallel c$ and $B \parallel ab$. The peculiar temperature dependence of "B_{c2}" can be explained by the Jaccarino-Peter compensation effect due to the antiferromagnetic exchange interaction between the Eu^{2+} moments and conduction electrons.

References

[1] Y. Kamihara *et al.*, J. Am. Chem. Soc. **130** (2008) 3296.
[2] M. S. Torikachvili *et al.*, Phys. Rev. Lett. **101** (2008) 057006.
[3] T. Park *et al.*, J. Phys.: Condens. Matter **20** (2008) 322204.
[4] P. L. Alireza *et al.*, J. Phys.: Condens. Matter **21** (2009) 012208.
[5] H. Fukazawa *et al.*, J. Phys. Soc. Jpn. **77** (2008) 105004.
[6] H. Kotegawa *et al.*, J. Phys. Soc. Jpn. **78** (2009) 013709.
[7] K. Igawa *et al.*, J. Phys. Soc. Jpn. **78** (2009) 025001.
[8] H. Lee *et al.*, Phys. Rev. B **80** (2009) 024519.
[9] C. F. Miclea *et al.*, Phys. Rev. B **79** (2009) 212509.
[10] T. Terashima *et al.*, J. Phys. Soc. Jpn. **78** (2009) 083701.
[11] K. Matsubayashi *et al.*, J. Phys. Soc. Jpn. **78** (2009) 073706.
[12] V. Jaccarino and M. Peter, Phys. Rev. Lett. **9** (1962) 290.
[13] M. Decroux and Ø. Fischer, in *Superconductivity in Ternary Compounds II*, eds. M. B. Maple and Ø. Fischer (Springer-Verlag, Berlin, 1982) Chap. 3.6.
[14] S. Jiang, Y. Luo, Z. Ren, Z. Zhu, C. Wang, X. Xu, Q. Tao, G. Cao, and Z. Xu, New J. Phys. **11** (2009) 025007.

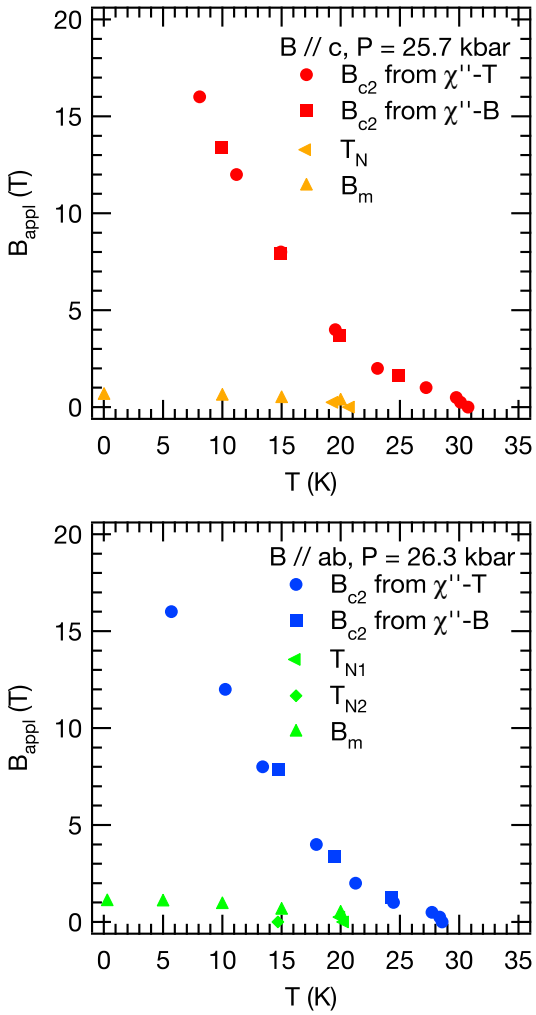

Figure 2: (Color online) B_{appl}-T phase diagrams of $EuFe_2As_2$.